

EFFECT OF TWO FORMULATIONS OF 10% SODIUM ASCORBATE ON FRACTURE RESISTANCE OF ENDODONTICALLY TREATED TOOTH SUBMITTED TO DENTAL BLEACHING WITH HYDROGEN PEROXIDE ASSOCIATED TITANIUM DIOXIDE NANOPARTICLES

ABSTRACT

PURPOSE: This study evaluated the effect of 10% sodium ascorbate (10SA), in gel (10SAg) or aqueous solution (10SAs) formulations, on fracture resistance of endodontically treated tooth submitted to dental bleaching procedures with 15% hydrogen peroxide associated with titanium dioxide (15HP-TiO₂) nanoparticles and photoactivated by LED-laser. **MATERIAL AND METHODS:** Forty maxillary premolars were endodontically-treated and embedded in acrylic resin up to the cement-enamel junction. The specimens were divided into four groups (n=10): G1 (negative control): no bleaching, coronal access restored with composite resin; G2 (positive control): three dental bleaching sessions using 15HP-TiO₂ and LED-laser photoactivation and restored with composite resin (positive control); G3 (10SAg): similar procedures to G2, but applied 10SA, in gel formulation, for 24 hours before restoration; G4 (10SAs): similar procedures to G3, but applied 10SA, in aqueous solution formulation. The 15HP-TiO₂ was applied on buccal and lingual surfaces of the crown tooth and inside the pulp chamber and photoactivated by LED-laser. Between each bleaching session, the teeth were maintained in artificial saliva, at 37°C, for 7 days. In sequence, the teeth were submitted to fracture resistance testing using an eletromechanical machine test. The data was analyzed using ANOVA test (p = 0.05) **RESULTS:** There are no differences significant among the groups in relation to fracture resistance of endodontically treated teeth (p>0.05). **CONCLUSIONS:** The use of 10% sodium ascorbate, in gel or aqueous solution formulations, did not interfered on the fracture resistance teeth after dental bleaching using 15HP-TiO₂ and LED-laser photoactivation.

BONTORIM, Francisco Carlos*

KUGA, Milton Carlos*

CIOFFI, Sabrina Spinelli*

SÓ, Marcus Vinicius Reis**

FARIA, Gisele*

PEREIRA, Jefferson Ricardo***

KEYWORDS

Tooth bleaching. Peroxides. Endodontics. Antioxidants. Tooth fractures.

PhD, Araraquara Dental School - Univ Estadual Paulista - UNESP, Araraquara, SP, Brazil*

PhD, Dental School, Rio Grande do Sul Federal University - UFRGS, Porto Alegre, RS, Brazil**

PhD, Dental School, University of Southern Santa Catarina - UNISUL, Tubarão, SC, Brazil***

Correspondence: miltoncarloskuga@hotmail.com (KUGA MC) | Received 12 Dec 2013 Received in revised form 16 Dec 2013 Accepted 20 Dec 2013

INTRODUCTION

The bleaching substances routinely used in endodontically treated teeth are hydrogen peroxide, carbamide peroxide, sodium perborate and sodium percarbonate.¹ These substances release free oxygen that diffuses into the dentin and/or enamel promoting discoloration of the substrate by an oxidation-reduction reaction.²⁻⁴ Hydrogen peroxide has a low molecular weight and at a high concentration is caustic and can damage the oral tissues and release free radicals in high quantity.^{1,5}

Dental bleaching can be accelerated by heat and photoactivation.⁵ Several light sources have been proposed, such as the LED (Light Emitted Diode)-laser system, which provide a highly selective and concentrated energy source.⁶ However, because the photoactivation did not substantially heat the hydrogen peroxide gel, the incorporation of dyes or pigments in the composition of the bleaching agent were proposed in order to more effectively absorb light and convert it into heat⁷.

The titanium dioxide (TiO_2) is an opaque inorganic pigment, chemically inert, thermally stable and with a high capacity to reflect light.⁸ Irradiated in a variable UV spectrum to blue visible light (approximately 380-450 nm), changes its electric charge providing destabilization of the hydrogen peroxide molecule.⁶ Its use is still

controversial, although there are reports that bleaching can be favored depending on the generation of oxidative radicals through TiO_2 photocatalysis⁹. However, it is demonstrated that the presence of TiO_2 , photoactivated by ultraviolet laser or LED-laser did not improve the esthetic results provided by the 35% H_2O_2 gel.⁸ Since the particle size of the pigment can also affect the results, the use of TiO_2 nanoparticles has recently been advocated.⁸ Therefore, the addition of TiO_2 in the hydrogen peroxide gel is still controversial and its effects on the tooth structure are still unknown.¹⁰

Several adverse effects caused by peroxides are described.¹ In particular, in endodontically treated teeth, there are reported interferences in the adhesion of restorative materials, risk of external resorption, changes in the structure of the enamel and dentin, increased dentin permeability and a reduction in the dentin microhardness.¹¹⁻²² However, the reduction of the fracture resistance of dental crowns after the use of bleaching agents, is one of the most controversial consequences.^{23,24} To minimize these adverse effects, the use of antioxidants before the final restoration has been recommended.^{25,26}

Sodium ascorbate is a neutral solution, antioxidant and biologically compatible, recommended to reverse the deleterious effects caused by oxidizing agents.²⁵⁻²⁷ When used after bleaching with 38% hydrogen

peroxide, it provides for the reestablishment of fracture resistance of endodontically-treated teeth.²⁸ However, its efficiency is directly related with the time application and/or formulation presentation to promote an efficient contact with the dentin submitted to bleaching protocols.²⁸⁻³⁰

Teeth immediately restored after crown bleaching with hydrogen peroxide in high concentrations have a lower fracture resistance.^{24,28} But it is unknown if the bleaching treatment with new agents using lower concentrations of hydrogen peroxide associated with titanium dioxide nanoparticles and photoactivated by LED-laser system, also reduce the fracture resistance of the endodontically-treated tooth. On the other hand, there are no studies that evaluate if the previous use of 10% sodium ascorbate, in liquid or gel formulation has a beneficial effect on the crown fracture resistance.

The aim of this study was to evaluate the effect on fracture resistance strength of endodontically treated teeth, after the use of 10% sodium ascorbate, in the liquid or gel formulation, in endodontically treated teeth submitted to bleaching with hydrogen peroxide with TiO₂ nanoparticles and a photoactivated LED-laser system. The null hypothesis was that 10% ascorbate sodium, in gel or aqueous solution, does not interfere in fracture resistance of endodontically treated teeth after dental bleaching using 15HP-TiO₂.

MATERIAL AND METHODS

After Human Research Ethics Committee approval, forty human premolars with similar anatomy, obtained from extractions for orthodontic reasons from patients 15 to 25 years old were used in this study. All teeth were stored in 0.1% thymol solution and maintained at 4°C. Previous to the utilization, the teeth were immersed in distilled water for complete removal of thymol residues for 24 hours and examined under a stereomicroscope magnification of 20x (Leica microsystems, Wetzlar, Germany) to exclude and replace those teeth with fracture/cracks lines or fissures.

After the access cavity preparation, the working length was determined subtracting 1mm from the root length using a #15 K-file (Maillefer, Ballaigues, Switzerland). The instrumentation was performed with a ProTaper system (Dentsply Maillefer, Ballaigues, Switzerland) up to a F2 instrumentation. The root canal were irrigated with 5 mL of 2.5% sodium hypochlorite solution (Clororio, São José do Rio Preto, SP, BR) between each change of instrument. In sequence, the smear layer was removed using 17% EDTA (Biodinamica Ind. Com, Ibiporã, PR Brazil), for 3 minutes and a final irrigation with 5 mL of 2.5% sodium hypochlorite was performed. The root canals were dried with absorbent paper points and obturated with AH Plus sealer (Dentsply DeTrey, Konstanz, Germany), using single cone technique. Radiographs were taken to verify the quality of the obturation.

A heated plugger (Touch'n Heat 5004; Sybron Endo, Orange, CA, USA) was used to remove 2 mm of gutta-percha from the root canal and glass ionomer cement (R Maxxion; FGM Dental Products Ltd., Joinville, SC, Brazil) was placed as a cervical

barrier. All teeth were embedded in polyester resin (Maxi Rubber, São Paulo, SP, Brazil) up to the cement-enamel junction, using a cylindrical plastic matrix (25 mm long x 19,5 mm in diameter). The specimens remained untouched for 24 hours, until complete resin polymerization.

The specimens were then divided into four groups (n=10), according to the following protocol: G1: unbleached (negative control), restored with an adhesive system (Scotchbond Multi-Purpose Adper Adhesive System, 3M ESPE, St Paul, MN, USA) and composite resin (Z100, 3M ESPE, St Paul, Mn USA). The access cavity was etched with 37% phosphoric acid (Condac 37; FGM Dental Products, Ltd., Joinville, SC, USA) for 15 seconds and then rinsed with a water spray for 10 seconds, leaving the dentin moist. In sequence, a adhesive system (Adper Scotchbond Multi-Purpose; 3M ESPE, St Paul, MN, USA), was applied to the dentin according to the manufacturer instructions and light cured (Ortholux™ LED Curing Light; 3M Unitek, Sumaré, SP, Brazil) for 20 seconds. The teeth were incrementally restored with composite resin (Z100, 3M ESPE, St Paul, MN, USA), applying 1.0 mm thick layers and light cured (Ortholux™ LED Curing Light; 3M Unitek, Sumaré, SP, Brazil) for 20 seconds, in each layer, until the complete filling of the pulp chamber.

In G2 (15HP-TiO₂, positive control): bleached with 15% H₂O₂ with TiO₂ nanoparticles (Lite Lase Peroxide 15%, DMC Equipment Ltd., São Carlos, SP, Brazil), photoactivated with a LED-laser system (Whitening lase II, DMC Equipment Ltd., São Carlos, SP, BR). After the manipulation of the product, in accordance to the manufacturer instructions, a layer of 2 mm of the gel was applied to the buccal and lingual surfaces of the crown tooth and photoactivated with a LED-laser system

(Whitening lase II; DMC Equipment Ltd., São Carlos, SP, BR) for 3 minutes. After the aspiration of the gel, a new application for 3 minutes was performed. An identical light application was also performed in the pulp chamber. Thus, each face was subjected to six minutes of photoactivation.

After the application and activation of the gel, all surfaces were abundantly washed with distilled water and two additional bleaching sessions, with intervals of 7 days between each, were performed. Between sessions, the pulp chambers were filled gutta percha and the coronal cavity was sealed with a temporary material (Coltosol; Vigodente SA Ind. Com., Rio de Janeiro, RJ, BR). All specimens were maintained in artificial saliva (Faculty of Pharmaceutical Sciences of Ribeirão Preto, University of São Paulo, Ribeirão Preto, SP, BR) during the study. After the conclusion of the bleaching procedures, the teeth were restored in the same manner as G1.

In G3 (10SAg), all procedures were realized similar to G2, but after the dental bleaching, the pulp chamber was filled with 10% sodium ascorbate in natrosol (Aphoticário, Araçatuba, SP, Brazil), for 24 hours, according previous recommendation.²⁸ After this period, the pulp chamber was washed with 5.0 mL distilled water, dried with an air stream and restored in a similar manner as described for G1. In G4 (10SAs), all procedures were realized similar to G3, but after the crown bleaching, the pulp chamber was filled with 10% sodium ascorbate solution (Aphoticário, Araçatuba, SP, Brazil).

After the restoration, the teeth were again maintained at 37°C and after 24 hrs submitted to fracture strength testing using an electromechanical testing machine EMIC DL 2000

(EMIC, São José dos Pinhais, PR, BR), at cross head speed of 0.5 mm/min. The test was carried out using a 5-mm diameter round bar positioned parallel to the long axis of the teeth and centered over the teeth until the bar just contacted the slopes of the buccal and lingual cusps of the tooth near the composite-tooth interface. The forces necessary to fracture each tooth were measured in KN. The moment of fracture was determined by a decrease in the force measurements in the testing machine. The data was statistically analyzed by the one-way ANOVA test ($p = 0.05$).

RESULTS


Figure 1 shows the means and standard deviations of the loads required (in KN) to fracture the crowns in each group. There are no significant statistical differences among the groups G1 ($0,75 \pm 0,43$ KN), G2 ($0,64 \pm 0,38$ KN), G3 ($0,71 \pm 0,18$ KN) and G4 ($0,75 \pm 0,47$ KN) evaluated in this study ($p > 0,05$).

DISCUSSION

The use of 10% sodium ascorbate, in the gel or liquid form, prior to the composite resin restoration in endodontically-treated teeth submitted to bleaching with 15% hydrogen peroxide associated with TiO₂ nanoparticles and photoactivated with LED-laser did not interfere in the fracture resistance teeth when compared to bleached or unbleached crowns and immediately restored. The null hypothesis was accepted.

In the current study, only the 15% peroxide hydrogen with TiO₂ photoactivated with LED-laser was evaluated. Although various techniques recommend using a combination of bleaching procedures, combining in-office and at-home bleaching procedures, only a single method to crown bleaching was used to avoid the interference of several techniques in the results.²⁸

Figure 1. Mean ultimate force required to fracture the endodontically treated teeth (KN). G1: unbleach teeth; G2 (15HP-TiO₂): 15% hydrogen peroxide with titanium dioxide and LED-laser photoactivation; G3 (10SAg): 10% sodium ascorbate gel; G4(10SAs): 10% sodium ascorbate solution. There are no difference between groups ($p > 0.05$).

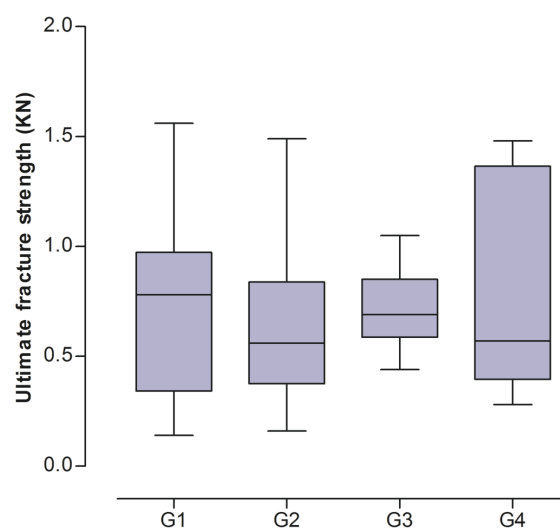

The use of sodium ascorbate is recommended for the reestablishment of the bond strength of esthetic restorative materials, after the use of bleaching agents.^{25,26,30} Free radicals released by hydrogen peroxide are

combined with the hydroxyapatite and produces peroxide apatite, which degrades the two main tooth mineral components, calcium and phosphate.³¹ On the other hand, the use of an antioxidant before the restoration provides a greater adhesion between the resin and tooth. When used for 24 hrs previous to the composite resin restoration, it significantly increased the fracture resistance of endodontically-treated teeth.²⁸

The protocol tested in the present study compared the use of gel or solution preparations, since the use of the gel preparation should be more practical and clinically more acceptable for applications.³² Despite different formulation, gel or liquid sodium ascorbate presentation did not increase the fracture resistance of the crowns.

The low hydrogen peroxide concentration used in present study possibly interfered in the results. The favorable effect of sodium ascorbate after dental bleaching apparently only is significant when used hydrogen peroxide in high concentration, which causes significant structural changes in dental structures.^{17,28}

Between the bleaching sessions any dental bleaching protocol was not used. This procedure may have interfered in the results, because when the 9.5% hydrogen peroxide was applied as an at-home treatment combined is observed a decrease of crown

resistance fracture.²⁸ On the other hand, the fact that none of the antioxidant protocols statistically differed for the controls groups, it may be also related to the dentin substrate characteristics and the time of the antioxidant application.^{30,32}

LED-laser system has a photo-thermal effect which is responsible for the activation of the pigments, providing a photocatalytic oxidation and increasing the temperature of the bleaching agent.³³ On the other hand, temperature elevation may exacerbate cracks and/or produce cracks that favor the fracture of the dental crown.³⁴ Since the TiO₂ used in the bleaching agent employed in this study, presented in the light spectrum sensitization variable 380-450 nm and the LED-laser device used generates blue light and infrared laser, with a respective wavelength of 470 nm and 808 nm, it is possible that the LED-laser system did not provide the appropriate effects on the TiO₂.^{6,8,35}

Further studies are still required to evaluate the effects of interaction between antioxidant (sodium ascorbate) and dental bleaching protocols on fracture resistance of endodontically treated teeth.

CONCLUSION

The use of 10% sodium ascorbate, in gel or aqueous solution formulation, for 24 hour after the dental bleaching protocol using 15% hydrogen

peroxide with titanium dioxide nanoparticles and photoactivated with LED-laser, before restoration with composite resin did not interfere on the fracture resistance of endodontically treated teeth.

REFERENCES

- Plotino G, Buono L, Grande NM, Pameijer CH, Somma F. Nonvital tooth bleaching: A review of the literature and clinical procedures. *J Endod.* 2008; 34: 394-407.
- McEvoy SA. Chemical agents for removing intrinsic stains from vital teeth. Part II Current techniques and their clinical application *Quintessence Int.* 1989; 20: 379-384.
- Joiner A. The bleaching of teeth: A review of the literature. *J Dent.* 2006; 34: 412-419.
- Chng HK, Ramli HN, Yap AU & Lim CT. Effect of hydrogen peroxide on intertubular dentine. *J Dent.* 2005; 33: 363-369.
- Chen JH, Xu JW, Shing CX. Decomposition rate of hydrogen peroxide bleaching agents under various chemical and physical conditions. *J Prosthet Dent.* 1993; 69: 46-48.
- Torres CRG, Borges AB, Kubo CH, Gonçalves SEP, Celaschi S, S GCE et al. *Clareamento dental com fontes híbridas LED/LASER.* São Paulo: Santos; 2007.
- Baik JW, Rueggeberg FA, Liewehr FR. Effect of light-enhanced bleaching on in vitro surface and intrapulpal temperature rise. *J Esthet Restor Dent.* 2001; 13: 370-378.
- Caneppele TMF, Torres CRG, Chung A, Goto EH, Lekevicius SC. Effect of photochemical activation of hydrogen peroxide bleaching gel with and without TiO₂ and different wavelengths. *Braz J Oral Sci.* 2010; 9: 393-397.
- Suyama Y, Otsuki M, Ogisu S, Kishikawa R, Tagami J, Ikeda M, Kurata H, Cho T. Effects of light sources and visible light-activated titanium dioxide photocatalyst on bleaching. *Dent Mat J.* 2009; 28: 693-699.
- Nonami T, Ishibashi K, Ishibashi T, Kondo O. Bleaching of TiO₂ photocatalyst: Part 1. Color alteration and microstructural changes by bleaching. *Jpn J Conserv Dent.* 2001; 44: 37-43.
- Josey AL, Meyers IA, Romaniuk K, Symons AL. The effect of a vital bleaching technique on enamel surface morphology and the bonding of composite resin to enamel. *J Oral Rehabil.* 1996; 4: 244-250.
- Kwon YH, Huo MS, Kim KH, Kim SK, Kim YJ. Effects of hydrogen peroxide on the light reflectance and morphology of bovine enamel. *J Oral Rehabil.* 2002; 29: 473-477.
- Shinohara MS, Peris AR, Pimenta LAF, Ambrosano GMB. Shear bond strength evaluation on composite resin on enamel and dentin after nonvital bleaching. *J Esthet Restor Dent.* 2005; 17: 22-29.
- Timpawat S, Nipattamanon C, Kijssamanmith K, Messer HH. Effect of bleaching agents on bonding to pulp chamber dentine. *Int Endo J.* 2005; 38: 211-217.
- Forner L, Salmerón-Sánchez M, Palomares M, Llana C, Amengual J. The use of atomic force microscopy in determining the stiffness and adhesion force of human dentin after exposure to bleaching agents. *J Endod.* 2009; 35: 1384-1386.
- Heller D, Skriber J, Lin LM. Effect of intracoronary bleaching on external cervical root resorption. *J Endod.* 1992; 18: 145-148.
- Zalkind M, Arwaz JR, Goldman A, Rotstein I. Surface morphology changes in human enamel, dentin and cementum following bleaching: a scanning electron

- microscopy study. *Endod Dent Traumat.* 1996; 12: 82-88.
18. Cavalli V, Shinohara MS, Ambrose W, Malafaia FM, Pereira PNR, Giannini M. Influence of intracoronal bleaching agents on the ultimate strength and ultrastructure morphology of dentine. *Int Endo J.* 2009; 42: 568-575.
19. Carrasco LD, Fröner IC, Corona SAM, Pécora JD. Effect of internal bleaching agents on dentinal permeability of non-vital teeth: quantitative assessment. *Dent Traumatol.* 2003; 19: 85-89.
20. Carrasco LD, Guerisoli DMZ, Pécora JD, Fröner IC. Evaluation of dentin permeability after light activated internal dental bleaching. *Dent Traumatol.* 2007; 23: 30-34.
21. Chng HK, Yap AUJ, Wattanapayungkul P, Sim CPC. Effect of traditional and alternative intracoronal bleaching agents on microhardness of human dentine. *J Oral Rehab.* 2004; 31: 811-816.
22. Oliveira DP, Teixeira ECN, Ferraz CCR, Teixeira FB. Effect of intracoronal bleaching agents on dentin microhardness. *J Endod.* 2007; 33: 460-462.
23. Kuga MC, Reis JMSN, Fabrício S, Bonetti-Filho I, Campos EA, Faria G. Fracture strength of incisor crowns after intracoronal bleaching with sodium percarbonate. *Dent Traumatol.* 2012; 28: 238-242.
24. Pobbe POS, Viapiana R, Souza-Gabriel AE, Marchesan MA, Sousa-Neto MD, Silva-Sousa YTC, Silva RG. Coronal resistance to fracture of endodontically treated teeth submitted to light-activated bleaching. *J Dent.* 2008; 36: 935-939.
25. Torres CRG, Koga AF, Borges AB. The effects of antioxidant agents as neutralizers of bleaching agents on enamel bond strength. *Braz J Oral Sci.* 2006; 5: 971-976.
26. Gökçe B, Çömlekoglu ME, Özpınar B, Türkün M, Kaya AD. Effect of antioxidant treatment on bond strength of a luting resin to bleach enamel. *J Dent.* 2008; 36: 780-785.
27. Cunha LF, Furue AY, Mondelli RFL, Mondelli J. Compromised bond strength after root dentin deproteinization reversed with ascorbic acid. *J Endod.* 2010; 36: 130-134.
28. Khoroushi M, Feiz A, Khodamoradi R. Fracture resistance of endodontically-treated teeth: Effect of combination bleaching and an antioxidant. *Oper Dent.* 2010; 35: 530-537.
29. Freire A, Souza EM, Caldas DBM, Rosa EAR, França C, Bordin W, Carvalho RM, Vieira S. Reaction kinetics of sodium ascorbate and dental bleaching. *J Dent.* 2009; 37: 932-936.
30. Türkün M, Celik EU, Kaya AD, Arici M. Can the hydrogel form of sodium ascorbate be used to reverse compromised bond strength after bleaching? *J Adhes Dent.* 2009; 11: 35-40.
31. Zhao H, Li X, Wang J, Qu S, Weng J, Zhang X. Characterization of peroxide ions in hydroxyapatite lattice. *J Biomed Mater Res.* 2000; 52: 157-163.
32. Sasaki RT, Flório FM, Basting RT. Effect of 10% sodium ascorbate and 10% α -tocopherol in different formulations on the shear bond strength of enamel and dentin submitted to a home-use bleaching treatment. *Oper Dent.* 2009; 34: 746-752.
33. Sydney GB, Barletta FB, Sydney RB. In vitro analysis of effects of heat used in dental bleaching on human dental enamel. *Braz Dent J.* 2002; 13: 166-169.
34. Tam LE, Kuo VY, Noroozi A. Effect of prolonged direct and indirect peroxide bleaching and fracture

toughness of human dentin. *J Esthet Restor Dent.* 2007; 19: 100-109.

35. Araujo FO, Baratieri LN, Araújo E. In situ study of in-office bleaching procedures using light sources on human enamel microhardness. *Oper Dent.* 2010; 25: 139-146